

SpinTek T_d Ceramic™ Membrane

Unique Ceramic Membrane


The SpinTek T_d ceramic membrane offers a new tool for the separation of micro-sized solids from liquid, gas and air influent. The unique T_d membrane starts as a 185 micron thick stainless steel substrate and then a thin (15 micron) nanopowder coating of ceramic is bonded to the substrate. The ceramic coating has a smooth surface that resists fouling which occurs with conventional “depth” type ceramic membranes. The T_d membrane is available in pore sizes as small as 0.07 microns and as large as 0.8 microns. The base ceramic of the T_d membrane is titanium dioxide (TiO₂) manufactured from nano-sized ceramic powders. This can be blended with either zirconia or with a composite of alumina and silica dioxide depending on the intended service.

Membrane Sizes

The SpinTek T_d membrane is available in square sheets 285 mm (11.2") x 285 mm (11.2"). Larger sheets are available by precision welding standard T_d sheets together. Standard circular and rectangular configurations are available and custom configurations can be laser cut to meet most needs. The T_d membrane can also be rolled to a minimum dimension of 10 mm (3/8") without damaging the membrane surface.

System Configurations

The T_d membrane can be used in the SpinTek ST-II and Speedy rotary microfiltration applications. Our engineers can also custom design and fabricate specific membrane modules for most applications.

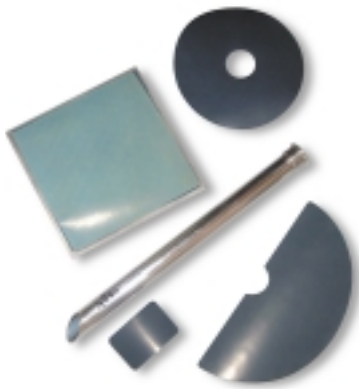

TiO₂ Membranes in Flat Sheet, Disk, "Half Moon," and 1" Tubular

Membrane


KEY BENEFITS

- 0.07 to 0.8 micron pore sizes can be specified
- 100% membrane stability in highly alkaline and solvent environments
- Operationally stable to 300°C in air and up to 800°C in an inert or reducing atmosphere
- Smooth membrane surface resists fouling
- Tight mean pore diameter for precise filtration
- Excellent performance in oil/water separation applications
- Titanium substrate available
- Resistant to bacterial attack
- Can be sterilized with live steam



SpinTek T_d Ceramic™ Membrane


Membrane

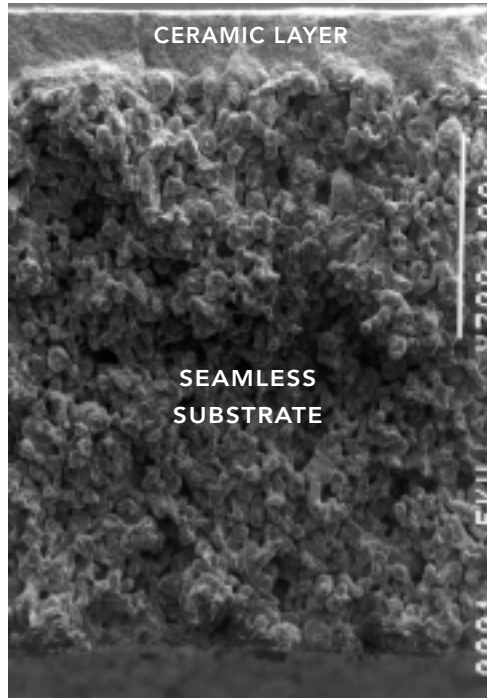

Scanning Electron Microscope (SEM) Image

Differential Flow Distribution

Argon Gas at 0.5 kg/cm² (7.1 psig) TMP

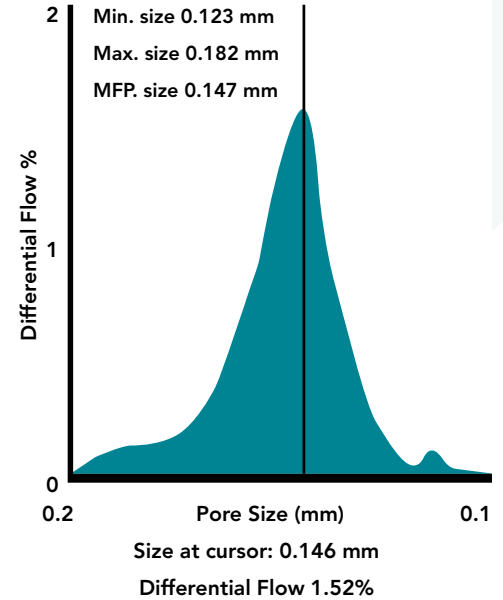

The Coulter Porometer II analysis demonstrates the tight pore distribution of the SpinTek T_d 0.15 micron membrane with a maximum pore of 0.182 mm and a minimum of 0.123 mm with 34 x10⁹ pores/cm² between maximum/minimum.

SpinTek T_d Membranes

Pore Size	Water Flow		Gas Flow	
	l/h·m ²	gpd/ft ²	l/h·m ²	scfm/ft ²
0.07	1,000	590	75,000	4.1
0.10	2,200	1,300	140,000	7.7
0.15	2,500	1,475	160,000	8.7
0.20	3,800	2,240	190,000	10.4
0.40	5,500	3,250	200,000	10.9
0.80	7,000	4,125	250,000	13.7

Water flow rate is distilled water at 2.0 kg/cm² (28.4 psig) TMP. Gas flow rate is Argon at 0.5 kg/cm² (7.1 psig) TMP.

SpinTekfiltration
10851 Portal Drive
Los Alamitos, CA 90720 USA

Telephone: 714-236-9190
Facsimile: 714-236-9196
Internet: www.spintekfiltration.com

 SpinTekfiltration
Advancing the flow of industry